

Derivation of the generalized Non Linear Sigma Model in the presence of the Dzyaloshinskii-Moriya interaction

L. Benfatto ^{a,*}, M. Silva Neto ^b, V. Juricic ^b C. Morais Smith ^b

^aSMC-INFM and Department of Physics, University of Rome "La Sapienza", Piazzale Aldo Moro 5, 00185, Rome, Italy

^bInstitute for Theoretical Physics, University of Utrecht, P.O. Box 80.195, 3508 TD, Utrecht, The Netherlands

Abstract

We derive the long-wavelength non-linear sigma model for a two-dimensional Heisenberg system in the presence of the Dzyaloshinskii-Moriya and pseudodipolar interactions. We show that the system is a non-conventional easy-axis antiferromagnet, displaying an anomalous coupling between the magnetic field and the staggered order parameter. Our results are in good agreement with recent experimental data for undoped La_2CuO_4 compounds.

Key words: LaCuO_4 , antiferromagnetism, non-linear sigma model

PACS: 74.25.Ha; 75.10.Jm; 75.30.Cr

It is well established that spin fluctuations play a prominent role in high-temperature superconductors. In particular, the parent compounds display an antiferromagnetic (AF) phase which is usually described as a two-dimensional (2D) Heisenberg antiferromagnet [1]. However, recent magnetic-susceptibility [2] and Raman [3] experiments in detwinned La_2CuO_4 (LCO) single crystals can not be understood within the theory of a conventional antiferromagnet. In Ref. [4] we argued that these anomalies originate from the presence, in the low-temperature orthorhombic (LTO) phase of LCO, of the anisotropic Dzyaloshinskii-Moriya (DM) and pseudodipolar (XY) interactions between spins. In this paper we derive explicitly the long-wavelength limit of the following 2D $S = 1/2$ Hamiltonian:

$$H = \sum_{\langle i,j \rangle} J \mathbf{S}_i \cdot \mathbf{S}_j + \mathbf{D}_{ij} \cdot (\mathbf{S}_i \times \mathbf{S}_j) + \mathbf{S}_i \Gamma_{ij} \mathbf{S}_j, \quad (1)$$

where $\mathbf{S}_i$ represent the Cu^{++} spins, J is the AF superexchange, and $\mathbf{D}_{ij}$ and Γ_{ij} are, respectively, the DM vectors and XY matrices [5]. In the (xyz) coordinate

system of Fig. 1 the DM vectors are oscillating between neighboring bonds with $\mathbf{D}_{AB} = (0, d, 0)$, and $\mathbf{D}_{AC} = (d, 0, 0)$, while the Γ matrices are constant and given by $\Gamma_{AB} = \text{diag}(\Gamma_1 + \Gamma_2, \Gamma_1 - \Gamma_2, \Gamma_3)$ and $\Gamma_{BC} = \text{diag}(\Gamma_1 - \Gamma_2, \Gamma_1 + \Gamma_2, \Gamma_3)$. Here d and $\Gamma_{1,2,3} > 0$ are of order 10^{-2} and 10^{-4} , respectively, in units of J [5]. To construct the long wavelength effective theory for the above Hamiltonian we decompose the unit vector $\Omega_i = \mathbf{S}_i/S$ at site $\mathbf{r}_i$ into its slowly-varying staggered and uniform components, $\Omega_i = e^{i\mathbf{Q} \cdot \mathbf{r}_i} \mathbf{n}_i + a \mathbf{L}_i$, where $\mathbf{Q} = (\pi, \pi)$ and a is the lattice parameter. The constraint $\Omega_i^2 = 1$ is enforced by $\mathbf{n}_i^2 = 1$ and $\mathbf{L}_i \cdot \mathbf{n}_i = 0$. Using this decomposition, the Heisenberg part of the Hamiltonian (1) has the standard form [6]

$$\mathcal{L}_{HJ} = J \sum_{\langle i,j \rangle} \mathbf{S}_i \cdot \mathbf{S}_j = \frac{JS^2}{2} \int d^2\mathbf{x} [(\nabla \mathbf{n})^2 + 8\mathbf{L}^2], \quad (2)$$

while the DM and XY terms are given by

$$\begin{aligned} \mathcal{L}_{DM} &= \sum_{\langle i,j \rangle} \mathbf{D}_{i,j} \cdot (\mathbf{S}_i \times \mathbf{S}_j) \\ &= \frac{4S^2}{a} \int d^2\mathbf{x} \mathbf{d}_+ \cdot (\mathbf{n} \times \mathbf{L}) \end{aligned} \quad (3)$$

and

* Corresponding author. Tel: +39-06-49694212 fax: +39-06-4957697

Email address: lara.benfatto@roma1.infn.it (L. Benfatto).

$$\mathcal{L}_{XY} = \sum_{\langle i,j \rangle} \mathbf{S}_i \Gamma_{ij} \mathbf{S}_j = -\frac{S^2}{a^2} \int d^2 \mathbf{x} \left[2\Gamma_+^{\alpha\beta} n_\alpha n_\beta + \right. \\ \left. - \frac{1}{2} a^2 \Gamma_{AB}^{\alpha\beta} (\partial_x n_\alpha \partial_x n_\beta) - \frac{1}{2} a^2 \Gamma_{BC}^{\alpha\beta} (\partial_y n_\alpha \partial_y n_\beta) \right]. \quad (4)$$

Observe that only the combination $\mathbf{d}_+ \equiv (\mathbf{D}_{AB} + \mathbf{D}_{AC})/2 = (d, d, 0)/2$, oriented along the a direction in the LTO coordinate system, and $\Gamma_+ = (\Gamma_{AB} + \Gamma_{AC})/2 = \text{diag}(\Gamma_1, \Gamma_1, \Gamma_3)$ enter the continuum limit of the model (1). Moreover, since $\Gamma_i \ll J$ we can neglect the anisotropic corrections in the second line of Eq. (4) to the $(\nabla \mathbf{n})^2$ term of Eq. (2). Using the fact that $\mathbf{n}^2 = 1$ we can rewrite the first term of Eq. (4) as $\mathcal{L}_{XY} = \text{const} + (2S^2/a^2) \int d^2 \mathbf{x} (\Gamma_1 - \Gamma_3) n_z^2$, which explicitly indicates that the properties of the model (1) only depend on the difference $\Gamma_1 - \Gamma_3 > 0$. To derive the Euclidean action of the model (1) we introduce the path-integral coherent states representation of the spin states, which in addition to the previous contributions gives rise to the (dynamical) Wess-Zumino term [6]

$$\mathcal{L}_{WZ} = \frac{-iS}{a} \int d^2 \mathbf{x} \mathbf{L} \cdot (\mathbf{n} \times \dot{\mathbf{n}}), \quad (5)$$

so that the partition function $Z = \int D\mathbf{n} \delta(\mathbf{n}^2 - 1) e^{-\mathcal{S}}$, with the action $\mathcal{S} = \int d\tau [\mathcal{L}_{HJ} + \mathcal{L}_{DM} + \mathcal{L}_{XY} + \mathcal{L}_{WZ}]$. After integration of the $\mathbf{L}$ fluctuations we obtain in the LTO coordinate system the following modified non-linear σ model (NLSM) ($\beta = 1/T$ and $\int = \int_0^\beta d\tau \int d^2 \mathbf{x}$):

$$\mathcal{S} = \frac{1}{2gc} \int \{ (\partial_\tau \mathbf{n})^2 + c^2 (\nabla \mathbf{n})^2 + D_+^2 n_a^2 + \Gamma_c n_c^2 \}. \quad (6)$$

The bare coupling constant g and spin velocity c are given by $gc = 8Ja^2$ and $c = 2\sqrt{2}JSa$, and we defined $\mathbf{D}_+ = \sqrt{2gcS^2/Ja^2} \mathbf{d}_+ = (2\sqrt{2}Sd)\mathbf{e}_a$ ($\mathbf{e}_a$ is the unit vector along the a direction) and $\Gamma_c = (4gcS^2/a^2)(\Gamma_1 - \Gamma_3) = 32JS^2(\Gamma_1 - \Gamma_3)$. Eq. (6) describes a 2D anti-ferromagnet with an easy axis along the b direction. Moreover, in the ordered AF phase the system displays also an *uniform* magnetization along the c direction. In fact, the saddle-point value for $\mathbf{L}$, calculated from the Euclidean action $\mathcal{S}$, is

$$\mathbf{L} = \frac{i}{8aSJ} (\mathbf{n} \times \dot{\mathbf{n}}) + \frac{1}{2Ja} (\mathbf{n} \times \mathbf{d}_+). \quad (7)$$

Thus, when $\langle \mathbf{n} \rangle = \sigma_0 \mathbf{e}_b$ we have $\langle \mathbf{L} \rangle = (1/8aSJ)(\sigma_0 \mathbf{e}_b \times \mathbf{D}_+ \mathbf{e}_a) = (\sigma_0 D_+/8aSJ) \mathbf{e}_c$.

We can extend the previous result in Eq. (6) for the case of a multi-layered quasi-2D system, with an exchange coupling $J_\perp$ along the c direction, by writing $\mathcal{S} \rightarrow (1/2gc) \sum_m \int \mathcal{L}_m$, where

$$\mathcal{L}_m = (\partial_\tau \mathbf{n}_m)^2 + c^2 (\nabla \mathbf{n}_m)^2 + \frac{c^2 J_\perp}{a^2 J} (\mathbf{n}_m - \mathbf{n}_{m+1})^2 +$$

$$+ D_+^{m2} n_{ma}^2 + \Gamma_c n_{mc}^2, \quad (8)$$

where $\mathbf{n}_m$ is the staggered magnetization in the m th layer. We note that for a layered system the vector $\mathbf{D}_+^m = (-1)^m D_+ \mathbf{e}_a$ alternates in sign between neighboring layers, giving rise also to the staggered order of the uniform $\mathbf{L}_m$ components, in agreement with the experiments [2,3].

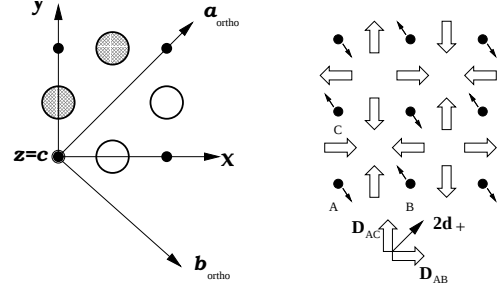


Fig. 1. Left: tetragonal (xyz) and orthorhombic (bac) reference system for the LCO plane. The hatched/empty circles represent the O^{2-} ions tilted above/below the CuO_2 plane. Right: arrangement of the staggered magnetization (small black arrows) and DM vectors (open arrows).

Finally, in the presence of an uniform magnetic field the total Lagrangian $\mathcal{L} = \mathcal{L}_{HJ} + \mathcal{L}_{DM} + \mathcal{L}_{XY} + \mathcal{L}_{WZ}$ acquires an additional term $\mathcal{L}_B = -(S/a) \int d^2 \mathbf{x} \mathbf{B} \cdot [\mathbf{L}_m - (\mathbf{L}_m \cdot \mathbf{n}_m) \mathbf{n}_m]$, where we made explicit the constraint $\mathbf{L}_m \cdot \mathbf{n}_m = 0$. This leads to an extra contribution $(1/8aJS)[\mathbf{B} - (\mathbf{B} \cdot \mathbf{n}_m) \mathbf{n}_m]$ to Eq. (7), which after integration over $\mathbf{L}_m$ has two effects on Eq. (6): (i) the modification $\partial_\tau \mathbf{n}_m \rightarrow \partial_\tau \mathbf{n}_m + i\mathbf{B} \times \mathbf{n}_m$ of the time derivative [7]; (ii) an additional term $(1/gc) \int \mathbf{B} \cdot (\mathbf{D}_+^m \times \mathbf{n}_m)$, for each layer. Observe that while the XY interaction only provides an easy-plane anisotropy for the standard Heisenberg system, via the $\Gamma_c n_c^2$ term of Eq. (6), the DM interaction gives rise to an *unconventional* coupling between the uniform magnetic field and the staggered magnetization. As discussed in detail in Ref. [4], this coupling is responsible for all the magnetic-susceptibility anomalies observed experimentally [2].

References

- [1] see M. A. Kastner *et al.*, Rev. Mod. Phys. **70**, 897 (1998) and references therein.
- [2] A. N. Lavrov *et al.*, Phys. Rev. Lett. **87**, 017007 (2001).
- [3] A. Gozar *et al.*, Phys. Rev. Lett. **93**, 027001 (2004).
- [4] M. B. Silva Neto, L. Benfatto, V. Juricic, and C. Morais Smith, cond-mat/0502588, to appear in Phys. Rev. B (2005).
- [5] L. Shekhtman *et al.*, Phys. Rev. Lett. **69**, 836 (1992); W. Koshibae *et al.*, Phys. Rev. B **50**, 3767 (1994).

- [6] I. Affleck, J. Phys. Cond. Matt. **1**, 3047 (1989).
- [7] S. Allen, D. Loss, Physica A **239**, 47 (1997).